


CCT diagrams

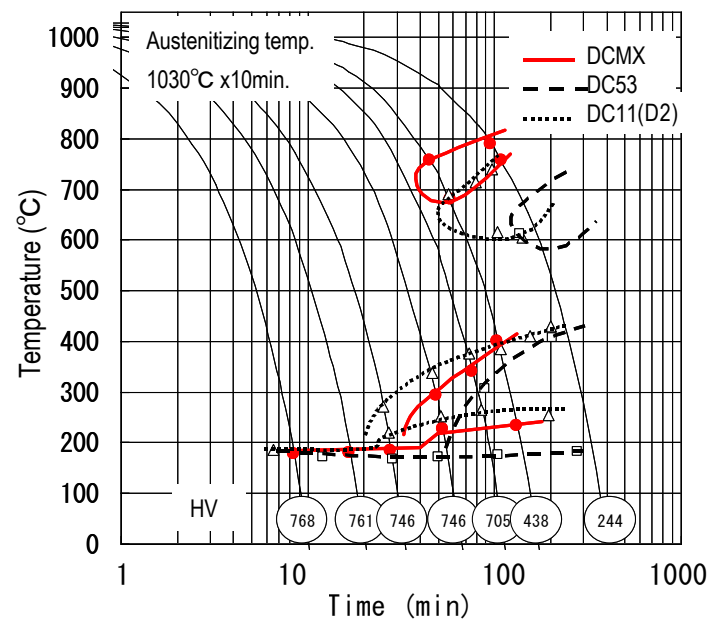

Physical properties

◆ Thermal expansion rate (x10 ⁻⁶ /K, Ave. value from 20°C)						
100°C	200°C	300°C	400°C	500°C	600°C	700°C
13.3	13.7	14.0	14.4	14.7	14.9	14.9
◆ Thermal conductivity (W/m·K [cal/cm·sec·°C])						
RT	100°C	200°C	300°C	400°C	500°C	
17.1	18.8	20.9	22.6	24.0	25.7	
[0.0409]	[0.0449]	[0.0499]	[0.0540]	[0.0573]	[0.0614]	
◆ Specific heat (J/kg·K)						
RT	100°C	200°C	300°C	400°C	500°C	
507	535	570	611	654	719	
◆ Young modulus = 202 GPa						
◆ Specific weight = 7.67 g/cm ³						
※ Heat treating of specimens						
Quenching: 1030°C, AC, Tempering: 500°C, Twice						

Comparison of properties among Daido cold work die steels

Properties		DCMX	DC53	DC11 (D2)
Tempering hardness	Low temp.(200°C)	61 HRC	61 HRC	61 HRC
	High temp.(500°C)	62 HRC	60 HRC	58 HRC
	High temp.(520°C)	60 HRC	62 HRC	58 HRC
Isotropy		◎	○	△
Dimensional change with time*1		○(○)	△(○)	○(○)
Hardenability		○	◎	○
Toughness		◎	○	△
Fatigue properties		◎	○	△
Machinability		◎	○	△
Wear resistance		◎	◎	○
Wear resistance to sand		△	○	◎
Wire EDM *2		○	◎	○
Low temp. coating *2		○	◎	○

*1 Comparison by dimensional change when stabilizing treated △:Average, ○:Good ◎:Excellent

Highlighted is especially featured properties

*2 Comparison by the decrease in hardness when tempered at 520°C for wire EDM and PVD coating



DAIDO STEEL

Tokyo Head Office
(Export Sales Dept.)
Daido Steel(America)Inc.

Daido Shinagawa Building, 6-35, 1-Chome, Konan, Minato-ku, Tokyo, Japan

Phone:+81-3-5495-1270 Fax:+81-3-5495-6738

1111 Plaza Drive, Suite 740, Schaumburg, IL 60173, U.S.A.

Phone:+1-847-517-7950 Fax:+1-847-517-7951

Bangkok Office

120 Moo 5, Wellgrow Industrial Estate, Bangna-Trad Road, KM.36, Bangsamak, Bangkok, Chachoengsao 24180, Thailand

Phone:+66-38-571317 Fax:+66-38-571313

Daido Steel (Shanghai) Co.,Ltd.

Room 1402, Ruijin Building, 205 Mao Ming Nan Road, Shanghai 200020, China

Phone:+86-21-5466-2020 Fax:+86-21-5466-0279

Daido Steel (Shanghai) Co.,Ltd.

Room 2601, No.8, Linhezong Road, Tianhe District, Guangzhou 510610, China

Guangzhou Subsidiary Company

Phone:+86-20-3877-1632 Fax:+86-20-8550-1126

IMPORTANT NOTE

Please be advised that Daido Steel shall not be held responsible for damage cause by misunderstanding or improper use of the technical information contained in this brochure.

The contents of this brochure may be subject to change without notice.

Please inquire of relevant department for the latest information.

No portion of this brochure may be reproduced without the express permission of Daido Steel.

Daido's Matrix type Tool Steels Series

DCMX

Matrix type Cold Work Die Steel

Features

DC-Matrix is a matrix type cold work tool steel: only fine carbides are distributed in matrix due to optimum alloy design and production process.
DC-Matrix shows high performance in service and ease in mold making as well.

<Die performance>

- ◆ **High hardness** such as 62HRC is available by high temperature tempering with good dimensional stability, resulting in high wear resistance.
- ◆ **High toughness** contributes to prevent cracking and chipping.

<Ease in die making>

- ◆ **Isotropic** dimensional change works easy geometry control in heat treating.
- ◆ **Machinability** is improved by free machining additives and finely dispersed carbides.

Main applications

- ◆ Punches, dies and working tools for cold pressing and cold forging, especially for Cold stamping dies for high strength steels where galling and peel off of coated layer, TD and CVD, are main failure modes
- Insert blocks for composite stamping dies where good dimensional stability is required in dies alignment
- Blanking punches and trimming edges where main failures are cracking and chipping.

Chemical composition

Patent pending

Heat treatment

Forging Temp.(°C)	Treating temperature (°C)				Hardness	
	Annealing	Quenching	Tempering	Stabilizing treatment	Annealed	Quenched & tempered
900—1160	920—980 Slow cooling	1000-1050 Air cooling	Low : 150 - 200 High: 480 - 560 Air cooling More than twice	400°C for longer than 1h	≤ 235HB	56~62HRC




DAIDO STEEL


Properties

Optical micrographs (As annealed)


● DCMX shows fine microstructure almost free from coarse carbides

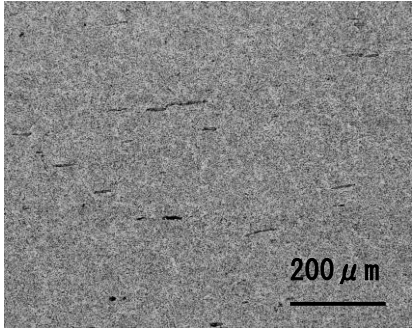

DCMX


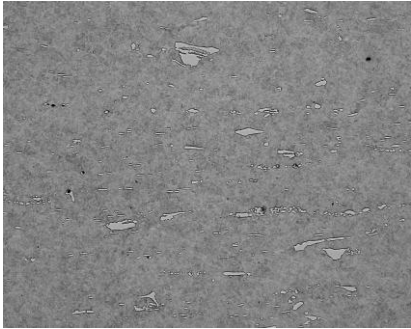


DC53

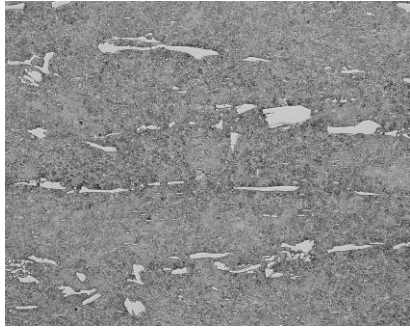


DC11 (Equivalent to D2)


Tempering hardness

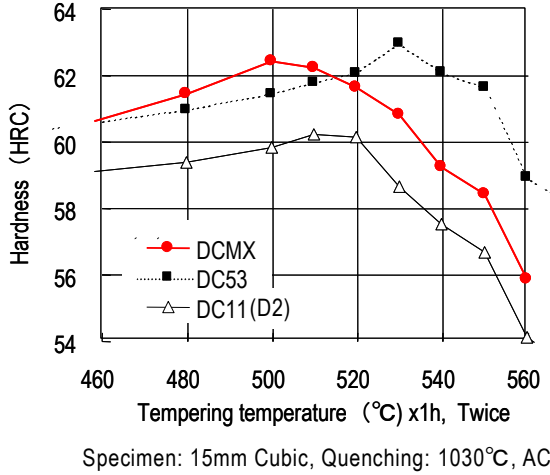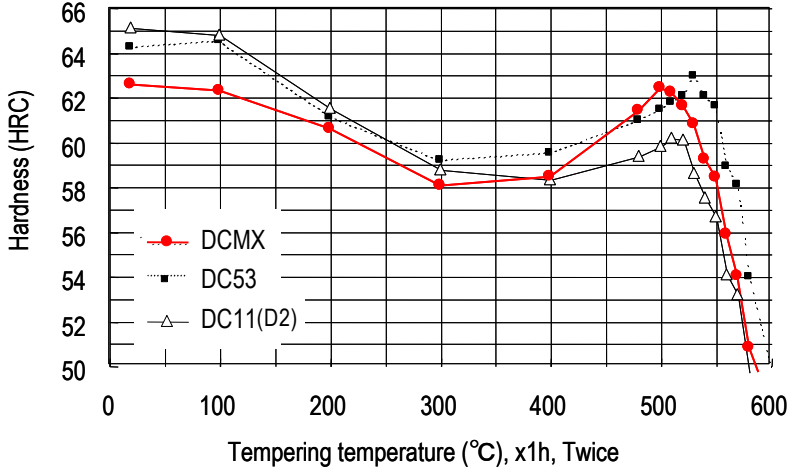

Dimensional stability

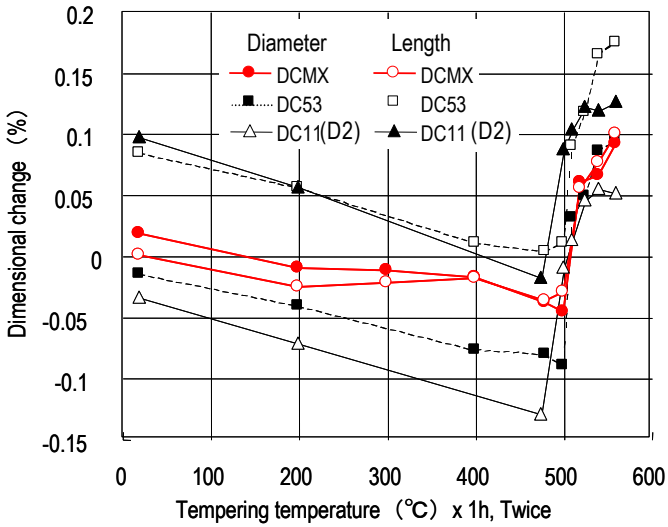


Specimen : 10mm dia. x 50mm Long
Quenching: 1030°C, AC

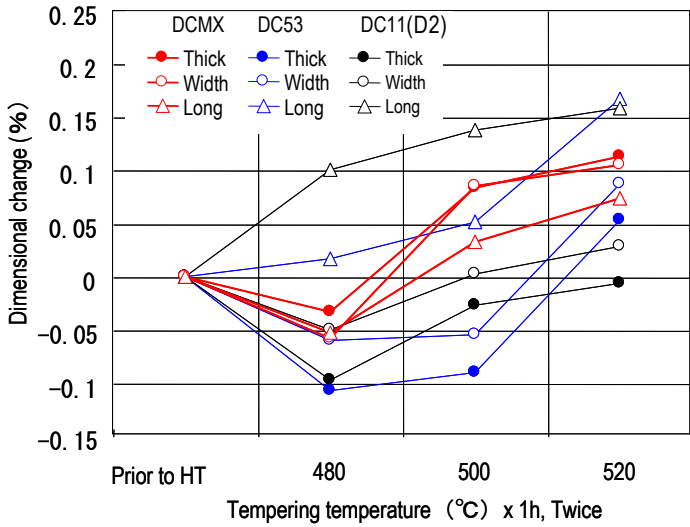


Specimen: 50mm Thick x 100mm Width x 150mm Long
Quenching: Atmosphere furnace, 1030°C, Fan AC



Toughness

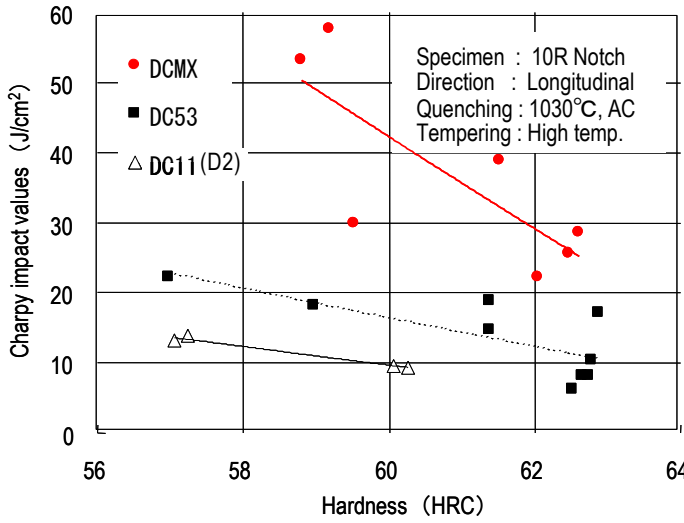


Fatigue properties

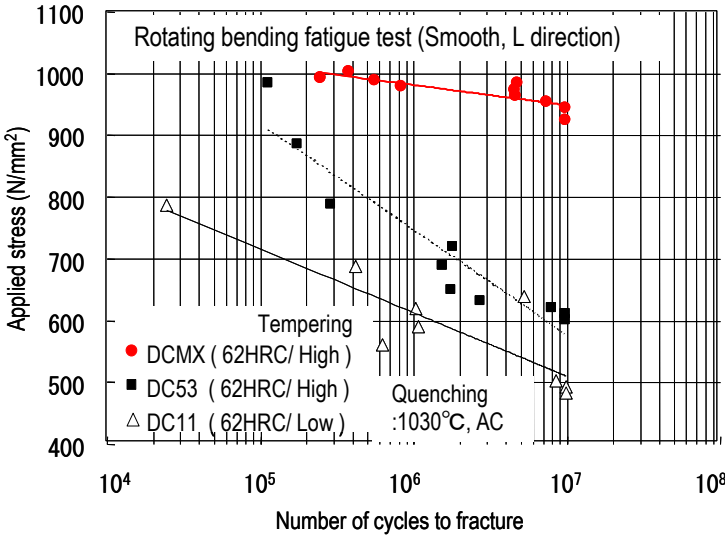


Machinability (Annealed)

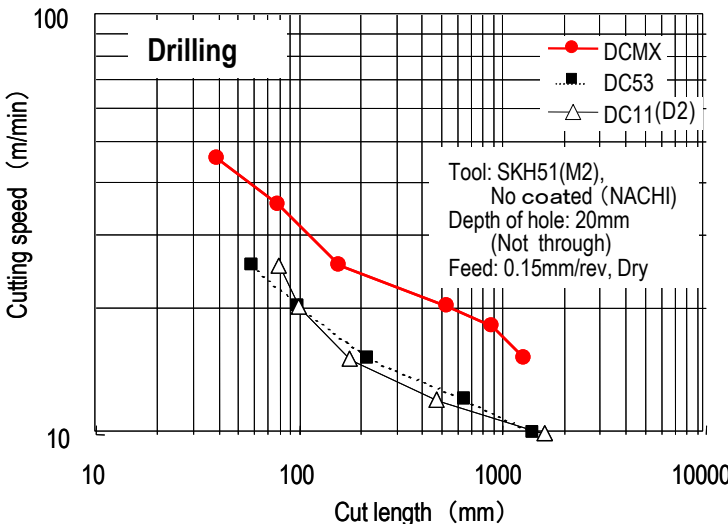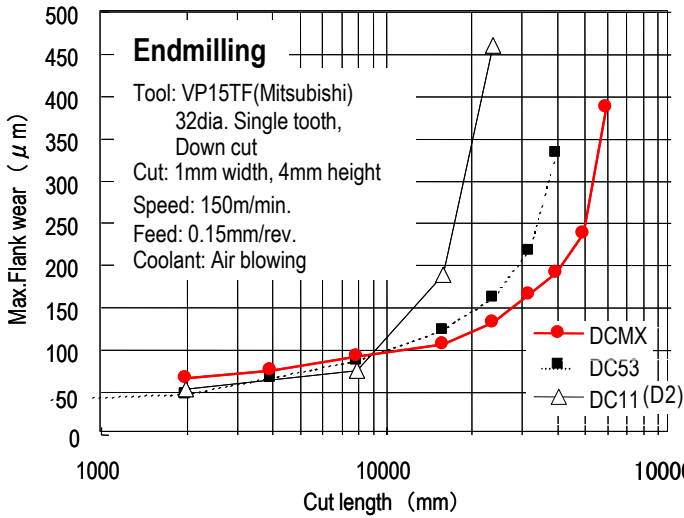

Wear resistance (Ohkoshi-test)

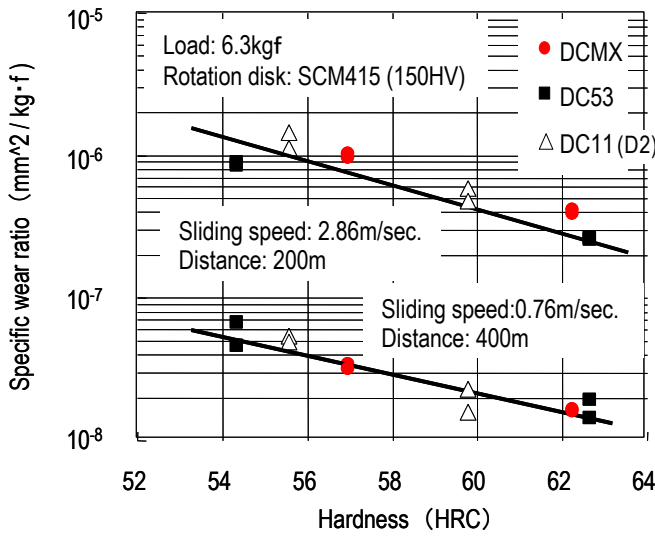

TD coating

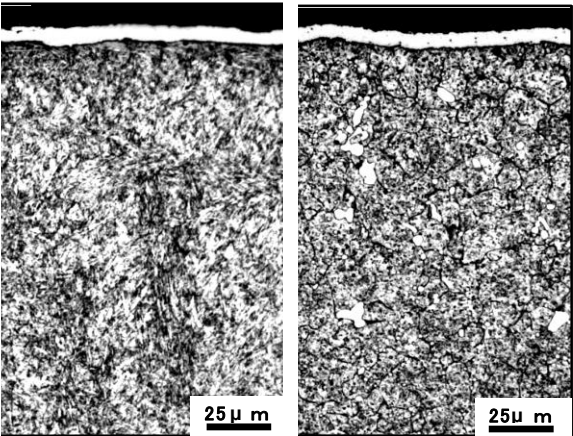

DCMX

DC11 (D2)

TD coating: By courtesy of DOWA Thermo Engineering.